

RESOLUTION NO. 81-55

A RESOLUTION OF THE CITY COUNCIL OF THE CITY OF RIDGECREST, CALIFORNIA, AMENDING RESOLUTION NO. 86 TO ADD STANDARD DRAWING AND SPECIFICATIONS FOR ROAD MIX ASPHALT SURFACE PAVEOUT REQUIREMENTS

WHEREAS, the City Council of the City of Ridgecrest, California, in Resolution No. 86 adopted "Standard Specifications" governing construction on public property; and

WHEREAS, the City Council wishes to amend said Resolution to add a Standard Drawing and Specifications for road mix asphalt surface paveout requirements;

NOW, THEREFORE, THE CITY COUNCIL OF THE CITY OF RIDGECREST, CALIFORNIA, RESOLVES AS FOLLOWS:

1. That Resolution No. 86 is hereby amended to add Standard Drawing and Specifications No. PS-2, a copy of which is attached hereto marked "Exhibit A" and made a part hereof by reference, and is hereby adopted as the Standard Specification of the City of Ridgecrest for road mix asphalt surface paveout requirements.
2. That the City Engineer is hereby directed to require construction of road mix asphalt surface paveouts in accordance with said Standard Drawing and Specification No. PS-2.

APPROVED AND ADOPTED this 4th day of November, 1981, by the following roll call vote:

AYES: Mayor Hockett, Vice-Mayor Bergens, Councilman Burnett and Councilman Grossman

NOES: None

ABSENT: Councilman Cheshire

ABSTAIN: None


HAROLD J. HOCKETT, Mayor

ATTEST:


JACQUELYNE C. REED, City Clerk

ROAD MIX ASPHALT SURFACE PAVEOUTS
SPECIFICATIONS

1. DEFINITION

Paveout is that area to be paved which is located between the lip (edge) of an existing or future gutter and the edge or near the edge of the existing roadway surface.

2. SCOPE OF WORK

This specification shall pertain to single family, multiple family, commercial and industrial paveouts.

3. MATERIALS

3.1 Asphalt shall be MC-800 (summer applications) or SC-800 (winter applications) at the rate of approximately 6% by weight and shall conform to Section 93 of the State of California Standard Specifications, latest edition.

3.2 Aggregate shall conform to the following Aggregate Grading Requirement:

<u>Sieve Size</u>	<u>Percentage Passing</u>
3/8"	100
No. 4	90-95
No. 8	80-86
No. 30	40-50
No. 200	0-20

or No. 4 maximum aggregate as identified in Section 39 of the State of California Standard Specifications, latest edition.

3.3 Asphaltic Tack Coat shall be CRS-2 and shall conform to the requirements of Section 94 of the State of California Standard Specifications, latest edition.

4. CONSTRUCTION REQUIREMENTS

4.1 General

4.1.1 The contractor shall notify the City Engineer at least 24 hours in advance of commencing any work.

4.1.2 Paveout must be constructed to provide a smooth transition with the existing pavement and shall provide positive drainage from the street to the gutter.

4.2 Subgrade

4.2.1 The contractor shall cut the existing road surface in a neat, straight line at the location specified by the City Engineer. Impact cutting device will be permitted.

4.2.2 Paveout area shall be excavated to the depth required as shown on the Asphalt Concrete Paveout Requirement Detail. (PS-1)

4.2.3 The subgrade material shall be compacted to a minimum relative density of 95%.

4.2.4 The depth of excavation and relative compaction of subgrade shall be approved by the City Engineer prior to the placement of road mix asphalt surface material.

4.3 Road Mix Asphalt Surface



4.3.1 Road Mix Asphalt shall be placed only when the atmospheric temperature is 60°F or above.

4.3.2 An asphaltic tack coat shall be applied to all joining surfaces.

4.3.3 The thickness of road mix asphalt surface material shall be as shown on the Road Mix Asphalt Surface Paveout Requirement Detail. (PS-2)

4.3.4 Road mix asphalt surface material shall be compacted using a steel-tired roller weighing not less than 3 tons which shall be self-propelled and reversible.

4.3.5 All work shall be completed according to adopted City standards and approved by the City Engineer.

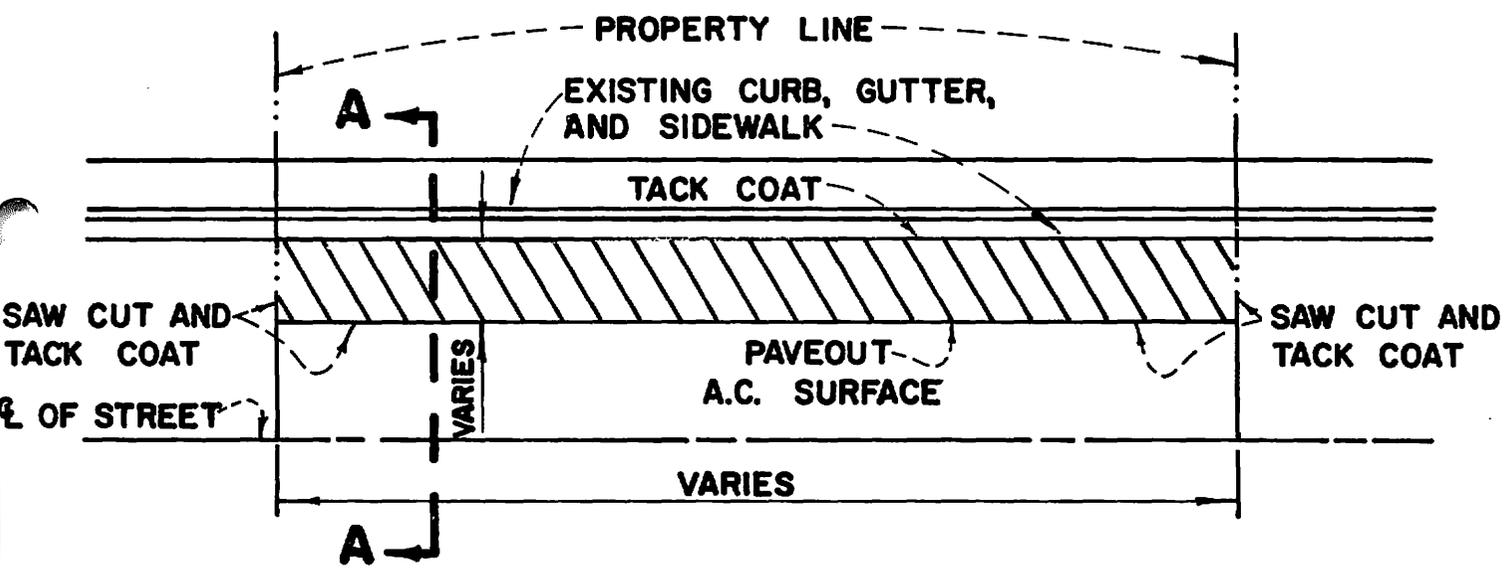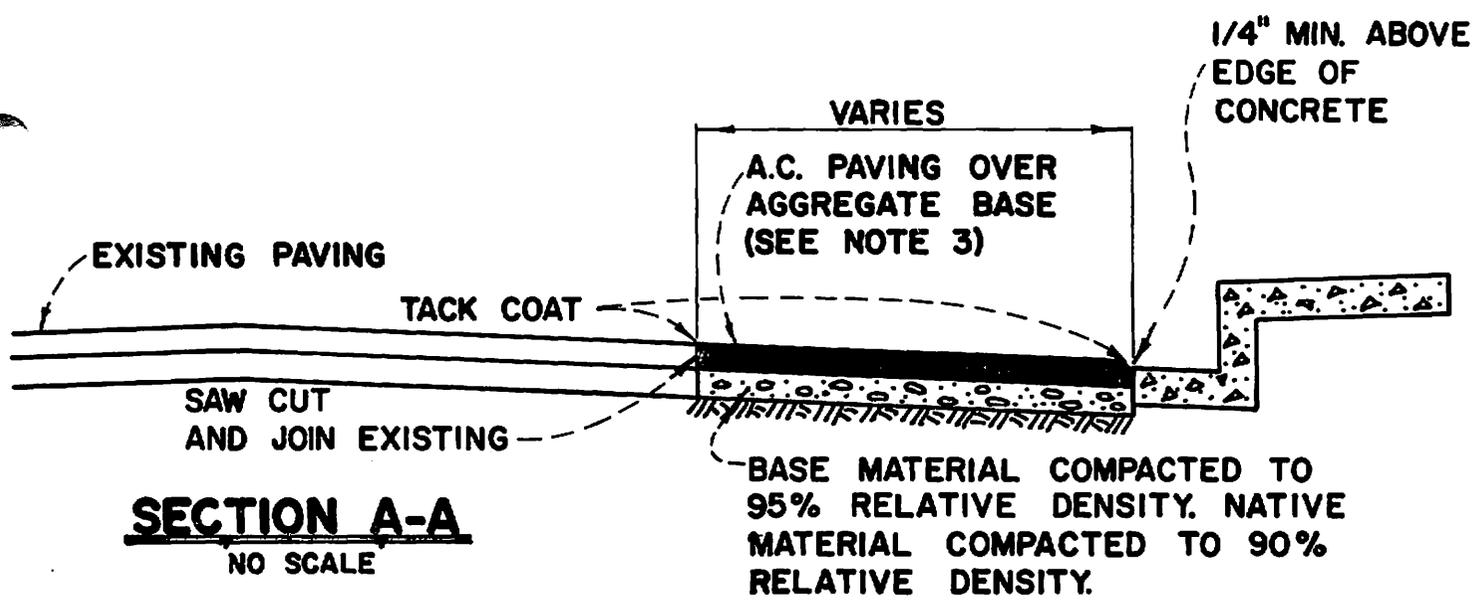

PLAN VIEW
NO SCALE

NOTE:

1. INSPECTION ON SUBGRADE AND AGGREGATE BASE REQUIRED BEFORE PAVING.
2. COMPACTION TESTING REQUIRED ON SUBGRADE AND AGGREGATE BASE WITH CONTRACTOR TO PAY FOR THE TEST(S).

3.

LAND USE	A.C.	AGG. BASE
SINGLE FAMILY RESIDENCE	2"	4"
MULTI FAMILY RESIDENCE	3"	6"
COMMERCIAL	3"	6"
INDUSTRIAL	3"	6"

APPROVED _____, 19____

CITY ADMINISTRATOR

APPROVED _____, 19____

CITY ENGINEER

DATE: 10-23-81
DRAWN: [Signature]
CHECKED: [Signature]

SCALE: NONE

ASPHALT CONCRETE PAVEOUT REQUIREMENTS

CITY OF RIDGECREST CALIFORNIA

No. PS-1